

## Pulsed $^1\text{H}$ NMR Relaxation in Crystalline Syndiotactic Polystyrene

Capitani D., Segre A.L., Grassi A., Sykora S.

Macromolecules **24**, 623-624 (1991)

This copy, scanned from an Author's reprint, is intended for personal perusal only.  
Other uses require permission of the *American Chemical Society*.

Other works by Stan Sykora can be found at [www.ebyte.it](http://www.ebyte.it)

This is a brief Note with no Abstract. Its main conclusions are:

- (i) The pulse  $^1\text{H}$  NMR technique is capable of discriminating between polymorphous polystyrenes.
- (ii)  $T_1$  relaxation gives a clear warning on the intensities used in CP-MAS techniques, regardless of contact times. Spectral intensity differences might be due to difference in proton relaxation times.
- (iii) An optimal temperature can be found, where the difference between  $T_1$  relaxations is the highest; at this temperature  $^{13}\text{C}$  CP-MAS might be carried out to give the best results.
- (iv) The value of the maxima defines a scale  $T_{1\delta} < T_{1\gamma} < T_{1\sigma} < T_{1\beta}$ . The order of this scale matches the solubility scale and solvent permeability of the four mesomorphous forms. Since  $\text{O}_2$  adsorption shortens  $T_1$  relaxation, it seems possible to correlate these values to the amount of sorbed  $\text{O}_2$ .

Keywords: NMR, LR NMR, Polymer, Polystyrene, Dissolved oxygen,  $T_1$ , Relaxation time, CP-MAS

### Pulsed $^1\text{H}$ NMR Relaxation in Crystalline Syndiotactic Polystyrene

Syndiotactic polystyrene can crystallize in four major crystalline modifications.<sup>1</sup> This complex polymorphism arises for two different reasons. The first derives from the conformation of the single macromolecule. In the  $\alpha$  and  $\beta$  forms<sup>2</sup> of syndiotactic polystyrene, the TT chain gives rise to macromolecules in a planar zigzag conformation, with a 5.1-Å identity period,<sup>1</sup> while, in the  $\gamma$  and  $\delta$  forms, a TTGG conformation was proposed on the basis of energy calculations.<sup>3</sup> These last two forms<sup>3,4</sup> have  $s(2/1)2$  symmetry and an identity period close to 7.7 Å.

The second cause of polymorphism is molecular packing; this is the origin of the structural difference between the  $\alpha$  and  $\beta$  forms.<sup>5-7</sup>

Due to varying  $\gamma$ -gauche contributions,<sup>8</sup>  $^{13}\text{C}$  CP-MAS NMR distinguishes clearly between polymers differing in the backbone conformation, but distinguishing polymorphs that have their origin only in molecular packing is rather ambiguous<sup>9</sup> and sometimes unsuccessful.<sup>10</sup>

Here we report a study of the four crystalline modifications of syndiotactic polystyrene by pulsed  $^1\text{H}$  NMR, the measured parameters being the spin-lattice relaxation times,  $T_1$  and  $T_{1\rho}$ , vs the temperature. The dependence of the spin-lattice relaxation time  $T_1$  on temperature for two polystyrene samples, one highly isotactic and the other highly syndiotactic ( $\gamma$ -form), is reported in Figure 1. Both samples were carefully degassed.

The usual progressive decay of  $T_1$  vs temperature can be seen; note that, on this basis, a distinction between the two polymers is not clear. In the temperature range 240–480 K the FID shows only one component, either lorentzian or gaussian or any combination of the two, depending on the temperature.<sup>11,12</sup> In the same range of temperature, the spin response to an inversion-recovery pulse sequence is a single exponential. Experiments at lower temperature are in progress. The dependence of  $T_1$  on temperature for the four polymorphous modifications of syndiotactic polystyrene is reported in Figure 2. All samples were undegassed. Since the four curves are well separated, a clear distinction between all four polymorphous forms can be observed. Note that the same measurements in well-degassed samples do not show any appreciable difference.

A large variation between degassed and undegassed aromatic polymers was previously observed by Froix et al.<sup>13-15</sup> This effect was attributed to the presence of  $\text{O}_2$  molecules adsorbed on the aromatic rings. In the case of syndiotactic polystyrenes, the  $\text{O}_2$  molecules act as a relaxation reagent that greatly affects the  $T_1$  relaxation values, while the absorption of  $\text{O}_2$  is modulated by the molecular packing. Thus, sorbed  $\text{O}_2$  allows NMR relaxation to distinguish between syndiotactic polystyrenes having polymorphism as a unique difference.

The behavior of  $T_{1\rho}$ , the relaxation in the rotating frame, vs the temperature is reported in Figure 3. The strong difference observed in the  $T_1$  plots is lacking, owing to the fact that  $T_{1\rho}$  is mostly sensitive to low-frequency motions. However, the  $\alpha$  form seems to relax faster than the other forms, probably because of some cooperative motion. All plots, in  $T_1$  and  $T_{1\rho}$ , collapse into a single plot at temperatures higher than the  $T_g$  ( $T_g \sim 90^\circ\text{C}$ ).<sup>16</sup> Their scattering can be regarded as a measure of the experimental error.

From all these data taken together, several conclusions may be drawn:

(i) The pulsed  $^1\text{H}$  NMR technique is capable of discriminating between polymorphous polystyrenes.

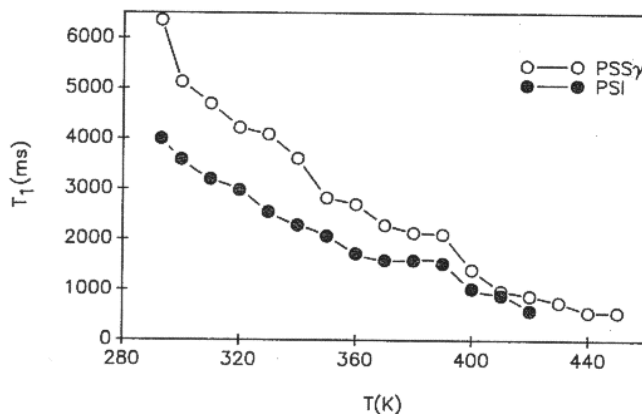


Figure 1.  $T_1$  as a function of the temperature for syndiotactic and isotactic polystyrene.

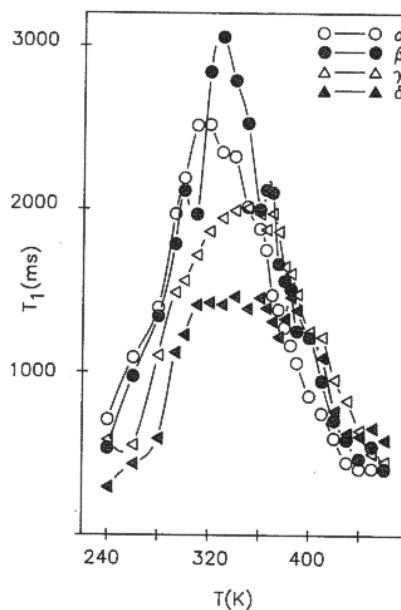


Figure 2.  $T_1$  as a function of the temperature for four crystalline modifications of syndiotactic polystyrene.

(ii)  $T_1$  relaxations give a clear warning on the intensities used in CP-MAS techniques regardless of contact times. Spectral intensity differences might be due to differences in proton relaxation times.

(iii) An optimal temperature can be found, where the difference between  $T_1$  relaxations is the highest; at this temperature (by means of properly tailored 2D experiments)  $^{13}\text{C}$  CP-MAS might be carried out to give the best results.

(iv) The value of the maxima (see Figure 2) defines a scale

$$T_{1\delta} < T_{1\gamma} < T_{1\alpha} < T_{1\beta}$$

The order of this scale strictly matches the solubility scale and solvent permeability of the four mesomorphous forms.<sup>17</sup> Since  $\text{O}_2$  adsorption shortens  $T_1$  relaxations, it seems possible to correlate these values to the amount of sorbed  $\text{O}_2$ .

Work is in progress to extend this study to the low-temperature range and to partially deuterated polymers.

**Experimental Section.** Syndiotactic polystyrene was prepared according to the literature,<sup>18</sup>  $\alpha$ ,  $\beta$ ,  $\gamma$ , and  $\delta$  polymorphs were crystallized and characterized by X-ray by Guerra and Corradini.<sup>2</sup>

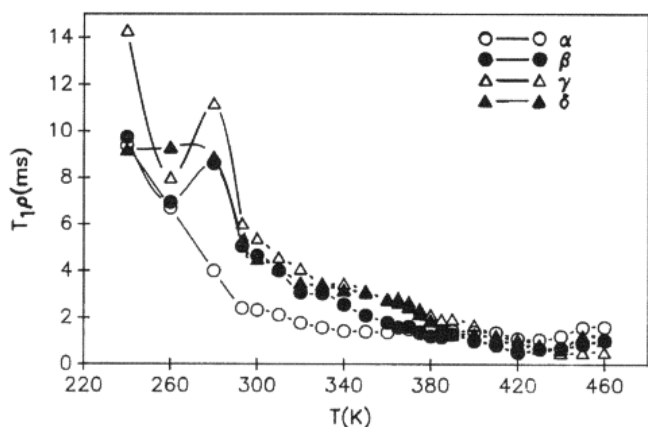


Figure 3.  $T_{1\rho}$  as a function of the temperature for four crystalline modifications of syndiotactic polystyrene.

Since the  $\delta$  form converts into other polymorphs,<sup>2</sup> NMR measures were carried out only at increasing temperatures.

Spin-lattice relaxation times,  $T_1$ , were measured at 30 MHz by a conventional inversion-recovery sequence with relaxation delays larger than  $5 T_1$ . Spin-lattice relaxation times in the rotating frame,  $T_{1\rho}$ , were measured at 40 kHz by a standard spin-locking sequence. The signal to noise ratio was improved by multiple scans (at least 32). The reported  $T_1$  values are the result of a three-parameter best fit procedure over at least 64 experimental points. In all measurements, experimental error is well within 10% of the reported value.

All low-resolution  $^1\text{H}$  NMR spectra were taken on a commercial spectrometer (Spinmaster, 4, 7- $\mu\text{s}$  90° pulse, 7- $\mu\text{s}$  dead time), equipped with a variable-temperature unit controller, from Stelar, Mede (PV), Italy.

**Acknowledgment.** Thanks are due to Prof. G. Guerra and Prof. P. Corradini for the X-ray powder spectra characterization and for useful discussions. The technical assistance of Miss P. Cafarelli is acknowledged. This work was supported by Progetto Chimica Fine II "Materiali Polimerici".

## References and Notes

- (1) Chatani, Y.; Fujii, Y.; Ijitsu, T. *Polym. Prepr. Jpn. (Engl. Ed.)* **1988**, *37*, E428.
- (2) Guerra, G.; Vitagliano, V. M.; De Rosa, C.; Petraccone, V.; Corradini, P. *Macromolecules* **1990**, *23*, 1539.
- (3) Corradini, P.; Napolitano, R.; Pirozzi, B. *Eur. Polym. J.* **1990**, *26*, 157.
- (4) Immirzi, A.; De Candia, F.; Iannelli, P.; Vittoria, V.; Zambelli, A. *Makromol. Chem., Rapid Commun.* **1988**, *9*, 761.
- (5) Corradini, P.; Guerra, G.; Pirozzi, B., to be submitted for publication.
- (6) Corradini, P. *Structural Order in Polymers*; Pergamon Press: Oxford, 1981; p 25.
- (7) Lovinger, A. J. *Developments in Crystalline Polymers*; Pergamon Press: Oxford, 1981; p 195.
- (8) Tonelli, A. E. *Macromolecules* **1983**, *16*, 604.
- (9) Brückner, S.; Meille, S. V.; Sozzani, P. IX Convegno Italiano di Scienza delle Macromolecole; Atti del Convegno, 1989, p 493.
- (10) Grassi, A.; Longo, P.; Guerra, G. *Makromol. Chem., Rapid Commun.* **1989**, *10*, 687.
- (11) Axelson, D. E.; Mandelkern, L.; Popli, R.; Mathieu, P. *J. Polym. Sci., Polym. Phys. Ed.* **1983**, *21*, 2318.
- (12) Axelson, D. E.; Mandelkern, L. *J. Polym. Sci., Polym. Phys. Ed.* **1983**, *21*, 29.
- (13) Froix, M. F.; Williams, D. J.; Goedde, A. O. *J. Appl. Phys.* **1975**, *46*, 4166.
- (14) Froix, M. F.; Williams, D. J.; Goedde, A. O. *Macromolecules* **1976**, *9*, 354.
- (15) Froix, M. F.; Williams, D. J.; Goedde, A. O. *Macromolecules* **1976**, *9*, 81.
- (16) De Candia, F.; Russo, R.; Vittoria, V. *J. Polym. Sci., Part C: Polym. Lett.* **1990**, *28*, 47.
- (17) Vittoria, V.; De Candia, F.; Iannelli, P.; Immirzi, A. *Makromol. Chem., Rapid Commun.* **1988**, *9*, 765.
- (18) Pellacchia, C.; Longo, P.; Grassi, A.; Ammendola, P.; Zambelli, A. *Makromol. Chem., Rapid Commun.* **1987**, *8*, 277.
- (19) CNR.
- (20) Università di Salerno.
- (21) Stelar s.n.c.

D. Capitani,<sup>\*,19</sup> A. L. Segre,<sup>19</sup> A. Grassi,<sup>20</sup> and S. Sykora<sup>21</sup>

Istituto Strutturistica Chimica, CNR  
M.B. 10, Monterotondo Staz., 00016 Roma, Italy  
Dipartimento di Fisica, Università di Salerno  
84100 Salerno, Italy  
Stelar s.n.c., via E. Fermi 4  
27035 Mede (PV), Italy

Received June 5, 1990

Revised Manuscript Received November 6, 1990